arXiv:cond-mat/0111457v3 [cond-mat.supr-con] 27 Mar 2002

Upper critical field in a trigonal unconventional superconductor UPt$_3$

P. L. Krotkov
L. D. Landau Institute for Theoretical Physics, Russian Academy of Sciences, 117334 Moscow, Russia

V. P. Mineev
Départament de Recherche Fondamentale sur la Matière Condensée,
Commisariat à l'Énergie Atomique, Grenoble 38054, France

(Dated: 1st February 2008)

A theory of the upper critical field in a trigonal superconductor with a two-component order-parameter is developed. We demonstrate the existence of sixfold modulations of the upper critical field in the basal plane. The form of the angular dependence of H_{c2} in the plane of the main symmetry axis is studied in the whole range of phenomenological rigidity coefficients. A qualitative dependence of these coefficients on the form of the Fermi surface is established. The results obtained are discussed in connection with the measurements of the direction dependence of H_{c2} in the heavy fermion superconductor UPt$_3$ that has been recently found to possess trigonal crystalline structure.

PACS numbers: 74.20.De, 74.70.Tx

I. INTRODUCTION

The heavy-fermion superconductor UPt$_3$ is traditionally held to be hexagonal. Based on high-energy x-ray diffraction and transmission electron microscopy, the crystal structure of UPt$_3$ have recently[1] been argued to be determined to be trigonal.

Trigonal deviations from the “ideal” hexagonal symmetry are of the order of 1%. That is why one can expect only small changes in the quantitative interpretation[2] of the numerous measurements of the thermodynamic and kinetic values based on the E_{2u} two-dimensional superconducting state. The same one can say in respect of the interpretation of the flux-line lattice experiment[3] proposed in Ref.[4]. It seems to be interesting however to concentrate efforts on the study of the properties that can demonstrate clear indubitable distinction between the two component superconductivity in hexagonal and trigonal crystals. The simplest example of such a property is orientational dependence of the upper critical field.

In the present article we develop Ginzburg-Landau theory of the orientational dependence of the upper critical field for a two-component superconducting state in a crystal with a trigonal symmetry. We demonstrate, in particular, that the upper critical field in a trigonal unconventional superconductor exhibits six-fold modulations in the basal plane, this conclusion remaining intact in the presence of an orthorhombic anisotropy in the direction fixed parallel or perpendicular to the magnetic field.

It is interesting to note that such small modulations (in experiments $|\delta H_{c2}^{hex}/H_{c2}| \lesssim 0.02$) have been observed in UPt$_3$ by angular resolved magnetoresistance measurements[5].

This experimental observation then encountered difficulty in explaining in the framework of any model of the superconducting phases in a hexagonal superconductor. Burlachkov[6] showed that $H_{c2}^{\perp}$ is isotropic for fields in the basal plane near T_c if the order parameter $\boldsymbol{\eta}$ transforms according to the two-dimensional irreducible representation E_1 of the hexagonal point group D_{6h}. He pointed out that $H_{c2}^{\perp}$ is also isotropic for E_2.

The hexagonal anisotropy in the GL functional then shows up only in the terms of the sixth order in gradients, giving that the resulting hexagonal anisotropy of $H_{c2}^{\perp}$ vanishes as $(1-T/T_c)^3$ near T_c just as it does in a hexagonal superconductor described by a one-component order parameter.

Shortly after the experiments[5], Mineev[7] demonstrated that in the model of two accidentally nearly degenerate 1D representations the hexagonal anisotropy of $H_{c2}^{\perp}$ also vanishes as $(1-T/T_c)^3$ near T_c.

Sauls[8] considered the hexagonal oscillations in the model of a two-dimensional representation for the superconducting order parameter coupled to an in-plane antiferromagnetic (AFM) order parameter $\mathbf{m}_s$. Large Zeeman energy oriented $\mathbf{m}_s$ near perpendicular to the external magnetic field. Hexagonal anisotropy of H$_{c2}$ then arose from the weak in-plane anisotropy energy of the AFM state through the coupling of the superconducting order parameter with $\mathbf{m}_s$.

On the other hand, the existence of the six-fold anisotropy $\propto (1-T/T_c)$ of the upper critical field in the basal plane of a trigonal crystal is quite natural, as we will see, and does not require any additional assumptions. It has been noticed for the first time numerically in the theoretical paper[9], the main goal of which was to study another type of anisotropy of the upper critical field — in the plane passing through the high-symmetry axis of an exotic trigonal superconducting monocrystal of Cu$_{1.8}$Mo$_6$S$_8$.

We also find the change of the form of H_{c2} in the plane of the main symmetry axis with the change of the parameters of the GL functional placing emphasis on the role of trigonality. We determine as well the qualitative dependence of the values of these parameters in the microscopic weak-coupling BCS theory on hexagonal and trigonal contributions to the shape of the Fermi surface.

The paper is organized as follows. In Sec. II we write out phenomenological GL differential equations on the spatial form of the order parameter used to find upper critical field in the basal plane in Sec. III and in the plane of the main symmetry axis in Sec. IV. The rigidity coefficients in the gradient energy of the GL functional are calculated microscopically in the weak-coupling BCS theory as functions of the initial trigonal anisotropies of the Fermi surface and the order parameter in Sec. V. Relevance of the theory to the experimental data known to date is discussed in the Discussions section VI.

II. GL EQUATIONS

In a trigonal crystal the GL functional up to terms of the second-order in the gradients and in the order parameter $\boldsymbol{\eta} = (\eta_1, \eta_2)$ has the form

$$\begin{aligned} \mathcal{F} &= \alpha|\boldsymbol{\eta}|^2 + \kappa_1|D_i\eta_j|^2 + \kappa_2|D_i\eta_i|^2 + \kappa_3(D_i\eta_j)(D_j\eta_i)^* \\ &+ \kappa_4|D_z\eta_i|^2 + \kappa_5\left((D_i\sigma^k_{ij}\eta_j)(D_z\eta_k)^* + \text{c.c.}\right), \end{aligned} \tag{1}$$

where

$$\alpha = \alpha_0(T - T_c)/T_c, \tag{2}$$

the covariant space derivatives

$$\boldsymbol{D} = -i\boldsymbol{\partial} + (2\pi/\Phi_0)\mathbf{A} \tag{3}$$

substitute the ordinary ones in the presence of the magnetic field $\mathbf{H} = \boldsymbol{\partial} \times \mathbf{A}$, σ^k is a vector $(\sigma^z, -\sigma^x)$ of the two Pauli matrices. $\Phi_0/2\pi = \hbar c/2e$ is the flux quantum.

The condition of the positive definiteness of the functional (1) requires that the following constraints on the coefficients are met (cf.[10])

$$\begin{aligned} \kappa_1 > |\kappa_3|, \quad \kappa_{123} &> 0, \quad \kappa_4 > 0, \quad \kappa_{123} + \kappa_2 > 0, \\ 2\kappa_5^2 &< \kappa_{13}\kappa_4, \end{aligned} \tag{4}$$

where, e.g., κ_{13} denotes $\kappa_1 + \kappa_3$.

The GL equation $\delta\mathcal{F}/\delta\boldsymbol{\eta}^* = 0$ is obtained by variation of the energy functional with respect to the order parameter. Before varying the functional (1) we note that the vector $(\sigma^z, -\sigma^x)$ of the two Pauli matrices has the property $\sigma^k_{ij}\eta_k = \sigma^j_{ik}\eta_k$ which can be checked directly. Using this the term proportional to κ_5 in the GL functional can be rewritten as

$$\kappa_5\left((D_i\sigma^k_{ij}\eta_j)(D_z\eta_k)^* + (D_z\eta_j)\sigma^k_{ij}(D_i\eta_k)^*\right). \tag{5}$$

Performing variation now we get

$$\begin{aligned} -\alpha\boldsymbol{\eta} &= \left(\kappa_1 D_i^2 + \kappa_4 D_z^2\right)\boldsymbol{\eta} + \left(\kappa_2\boldsymbol{D}D_i + \kappa_3 D_i\boldsymbol{D}\right)\eta_i \\ &+ \kappa_5\left(D_zD_i + D_iD_z\right)\boldsymbol{\sigma}_{ij}\eta_j. \end{aligned} \tag{6}$$

III. H_{c2} IN THE BASAL PLANE

For the magnetic field directed along the unit vector $\hat{\mathbf{n}} = (\cos\varphi, \sin\varphi, 0)$ in the basal plane it is convenient to choose the gauge of the vector potential in the form $\mathbf{A} = -Hz\hat{\boldsymbol{\tau}}$, where $\hat{\boldsymbol{\tau}} = \hat{z} \times \hat{\mathbf{n}}$. Then we may seek for solutions of equation (6) dependent only on z and hence put $\boldsymbol{D} = (2\pi/\Phi_0)\mathbf{A}$ and $D_z = -i\partial_z$ in (6). Measuring distances in units of the length $\sqrt{\Phi_0/2\pi H}$ and denoting

$$\lambda = -\alpha\Phi_0/2\pi H, \tag{7}$$

we arrive at:

$$\begin{aligned} \lambda\boldsymbol{\eta} &= \left(-\kappa_4\partial_z^2 + \kappa_1 z^2\right)\boldsymbol{\eta} + \kappa_{23}z^2\hat{\boldsymbol{\tau}}\left(\hat{\boldsymbol{\tau}}\boldsymbol{\eta}\right) \\ &+ i\kappa_5\hat{\tau}_i\boldsymbol{\sigma}_{ij}(1 + 2z\partial_z)\eta_j. \end{aligned} \tag{8}$$

Rotating vector $\boldsymbol{\eta}$ in the basal plane by the angle φ, i.e. changing variables from η_1, η_2 to $\eta_\parallel = \hat{\mathbf{n}}\boldsymbol{\eta}, \eta_\perp = \hat{\boldsymbol{\tau}}\boldsymbol{\eta}$, we finally get the system of two second order linear ordinary differential equations

$$\begin{aligned} \lambda\boldsymbol{\eta} &= -\kappa_4\partial_z^2\boldsymbol{\eta} + \begin{pmatrix} \kappa_1 & 0 \\ 0 & \kappa_{123} \end{pmatrix} z^2\boldsymbol{\eta} \\ &+ i\kappa_5\begin{pmatrix} -\sin 3\varphi & -\cos 3\varphi \\ -\cos 3\varphi & \sin 3\varphi \end{pmatrix}(1 + 2z\partial_z)\boldsymbol{\eta}. \end{aligned} \tag{9}$$

In a hexagonal superconductor $\kappa_5 = 0$ and equations on $\eta_\parallel$ and $\eta_\perp$ decouple, each being a Schrödinger equation of a harmonic oscillator with its own rigidity coefficient

$$\left(-\kappa_4\partial_z^2 + \kappa_1 z^2\right)\eta_\parallel = \lambda_\parallel\eta_\parallel, \tag{10}$$

$$\left(-\kappa_4\partial_z^2 + \kappa_{123} z^2\right)\eta_\perp = \lambda_\perp\eta_\perp. \tag{11}$$

Its eigenvalues with the boundary condition of vanishing at infinity are

$$\lambda_\parallel = \sqrt{\kappa_1\kappa_4}(2n + 1), \tag{12}$$

$$\lambda_\perp = \sqrt{\kappa_{123}\kappa_4}(2n + 1). \tag{13}$$

When lowering H at a fixed temperature $T < T_c$ (which corresponds to raising λ), the solution realizes for the first time at the lowest lying level λ_n at $n = 0$. I.e., a nucleus of the superconducting phase appears for the first time at

$$H_{c2\parallel} = \frac{\Phi_0}{2\pi}\frac{\alpha_0}{\sqrt{\kappa_1\kappa_4}}\frac{T_c - T}{T_c} \tag{14}$$

if $\kappa_{23} > 0$ (and then it is a phase with the order parameter $\boldsymbol{\eta}$ parallel to the direction of the applied field), or at

$$H_{c2\perp} = \frac{\Phi_0}{2\pi}\frac{\alpha_0}{\sqrt{\kappa_{123}\kappa_4}}\frac{T_c - T}{T_c} \tag{15}$$

if $\kappa_{23} < 0$, and then it is a nucleus of the phase with $\boldsymbol{\eta} \perp \mathbf{H}$. In any case, neither (14) nor (15) depends on the direction of the field, so the upper critical field is rotationally invariant in the basal plane[6].

In a trigonal crystal the coefficient κ_5 is non-zero, and the two equations in (8) cannot be decoupled by a rotation of the coordinate axes. The influence of the term proportional to κ_5 can be taken into account as perturbation.

Unfortunately, this does nor lead to a concise analytical expression. The reason is that in first order of perturbation theory the correction to the ground state eigenvalue of the system (9) is given by the averaging of the perturbation operator $\propto \kappa_5$ over the unperturbed ground state $(\psi_0(z, \sqrt{\kappa_1/\kappa_4}), 0)$ or $(0, \psi_0(z, \sqrt{\kappa_{123}/\kappa_4}))$ depending on the sign of κ_{23}. Here

$$\psi_0(z, A) = (A/\pi)^{1/4} e^{-Az^2/2} \tag{16}$$

is the ground state of the Schrödinger Eq. (10) or (11). The average of the operator $1+2z\partial_z$ over the state (16) is zero. So one need to account for second order corrections, which involve an infinite sum of matrix elements of the operator $1 + 2z\partial_z$ between zeroth (16) and higher lying states.

One can, however, accomplish perturbational calculations *with respect to the parameter* κ_{23}, with κ_5 generally staying arbitrary. Then one can obtain expressions for the limit $\kappa_5, \kappa_{23} \ll \kappa_1$ (see Table I for values of the coefficients κ_{23}, κ_5 in a BCS theory).

One proceeds by noting that in either of the cases $\kappa_{23} = 0$ or $\kappa_5 = 0$ by some rotation of the coordinate axes the two equations (8) decouple. So in both cases the upper critical field corresponds to the lower of the eigenvalues of the ground states of the two equations.

Rotating the coordinate system of Eq. (9) by $-\pi/4 - 3\varphi/2$, one arrives at

$$\begin{aligned} \lambda\boldsymbol{\eta} &= \left(-\kappa_4\partial_z^2 + \kappa_1 z^2\right)\boldsymbol{\eta} + i\kappa_5 \begin{pmatrix} 1 & 0 \\ 0 & -1 \end{pmatrix} (1+2z\partial_z)\boldsymbol{\eta} \\ &+ \frac{\kappa_{23}}{2} z^2 \begin{pmatrix} 1+\sin 3\varphi & -\cos 3\varphi \\ -\cos 3\varphi & 1-\sin 3\varphi \end{pmatrix} \boldsymbol{\eta}. \end{aligned} \tag{17}$$

In the zeroth order in κ_{23} the two equations decouple and with the help of the substitution

$$\eta_1(z) = e^{i\frac{\kappa_5}{\kappa_4}\frac{z^2}{2}}\eta_1(z), \quad \eta_2(z) = e^{-i\frac{\kappa_5}{\kappa_4}\frac{z^2}{2}}\eta_2(z) \tag{18}$$

reduce both to

$$\left(-\kappa_4\partial_z^2 + \kappa_1 R^2 z^2\right)\eta = \lambda\eta, \tag{19}$$

where we introduced the notation

$$R = \sqrt{1 - \kappa_5^2/\kappa_1\kappa_4}. \tag{20}$$

So that the ground state with the eigenvalue

$$\sqrt{\kappa_1\kappa_4}R \equiv \sqrt{\kappa_1\kappa_4 - \kappa_5^2} \tag{21}$$

is twice degenerate with the wave functions

$$\left(e^{i\frac{\kappa_5}{\kappa_4}\frac{z^2}{2}}\psi_0(z, R\sqrt{\tfrac{\kappa_1}{\kappa_4}}), 0\right), \quad \left(0, e^{-i\frac{\kappa_5}{\kappa_4}\frac{z^2}{2}}\psi_0(z, R\sqrt{\tfrac{\kappa_1}{\kappa_4}})\right). \tag{22}$$

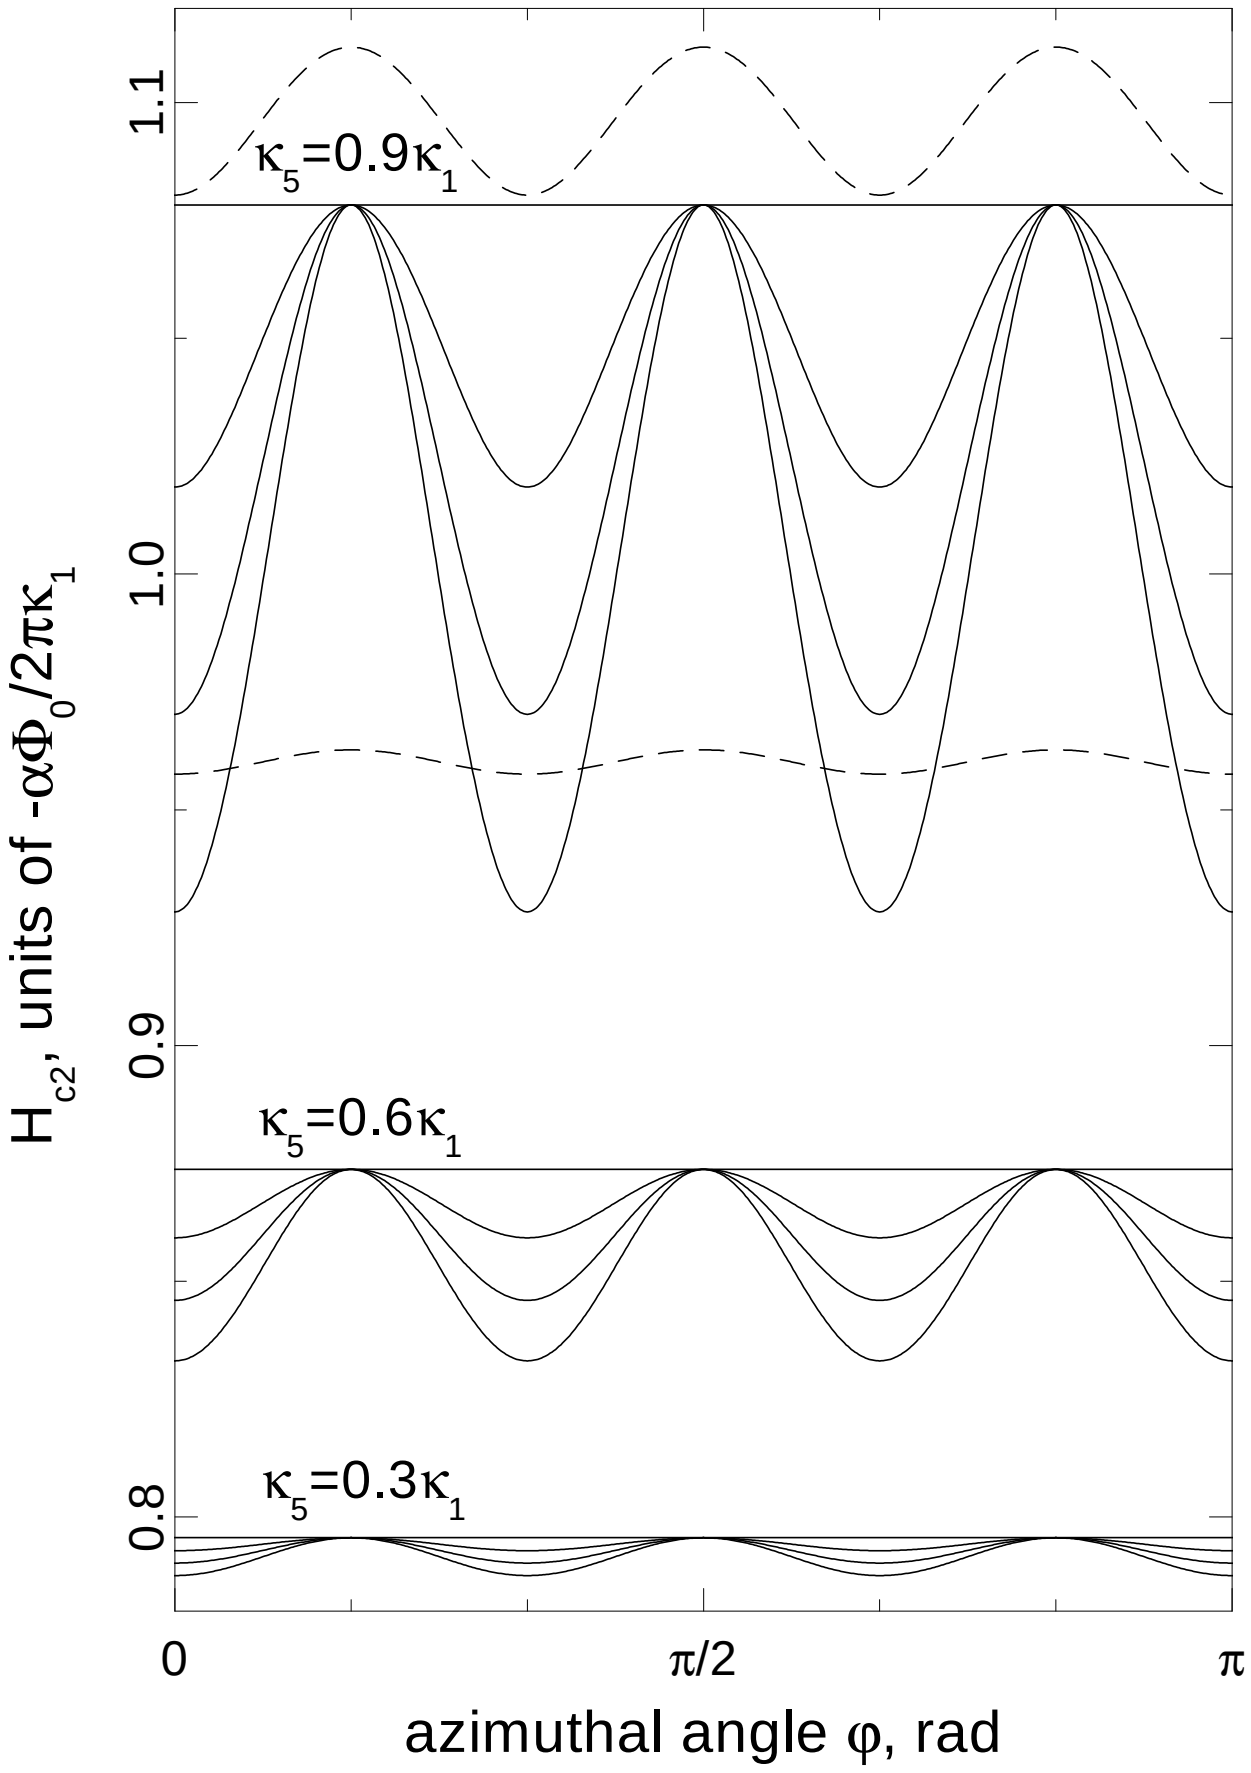

Figure 1: Upper critical field in the basal plane of a two-component trigonal superconductor for several values of the coefficients κ_3 and κ_5. See explanations in the text.

Using the first order theory of perturbation of a degenerate level, we find

$$H_{c2} = \frac{H_{c2\|}}{R\left[1 + \dfrac{\kappa_{23}}{4\kappa_1}\dfrac{1 \pm \sqrt{\sin^2 3\varphi + R^3\cos^2 3\varphi}}{R^2}\right]}, \tag{23}$$

where one should take sign plus for $\kappa_{23} < 0$ and sign minus for $\kappa_{23} > 0$.

We recall that this formula is valid for small $\kappa_{23} \ll \kappa_1$ and arbitrary κ_5. For small κ_5 and small κ_{23} we get by expansion that the first term dependent on φ is

$$-\frac{3}{16}H_{c2\|}\frac{|\kappa_{23}|}{\kappa_1}\frac{\kappa_5^2}{\kappa_1\kappa_4}\cos^2 3\varphi \tag{24}$$

while the constant part of H_{c2} acquires additional terms $O(\kappa_{23}/\kappa_1)$ and $O(\kappa_5^2/\kappa_1\kappa_4)$.

Eq. (24) shows that six-fold modulations of the upper critical field in a trigonal crystal have very small amplitude for small κ_{23} and κ_5, while their maxima occur at $\varphi = (2n+1)\pi/6$ (i.e., at directions of $\mathbf{H} \parallel \mathbf{a}^*$) irrespective of the signs of κ_{23} and κ_5.

Numerical calculations confirm these conclusions. They also show that the dependence $H_{c2}(\varphi)$ rests smooth, “sinusoidal” for almost all values of the rigidity coefficients except for both κ_{23} and κ_5 large — each close to the upper limit of its domain of definition (4), when the maxima of $H_{c2}(\varphi)$ at $\varphi = (2n+1)\pi/6$ become sharp.

On Fig. 1 we presented several curves $H_{c2}(\varphi)$ obtained numerically for $\kappa_4 = 1.67\kappa_1$ and several κ_{23}, κ_5: 3 groups of solid lines show curves for $\kappa_5 = 0.3\kappa_1$, $0.6\kappa_1$, and $0.9\kappa_1$ respectively from bottom to top. Inside each group 4 curves correspond to $\kappa_3 = 0$, $0.2\kappa_1$, $0.5\kappa_1$, and $0.999\kappa_1$ (from the upper line down to the lower). Two dashed lines display $H_{c2}(\varphi)$ for $\kappa_3 = -0.15\kappa_1$ and $\kappa_5 = 0.3\kappa_1$ (the lower of the dashed curves) and $0.6\kappa_1$ (the upper).

An alternative variational method of finding sinusoidal corrections (24) to the upper critical field, which also provides some insight into the behavior of H_{c2} in a variant of the GL theory with an orthorhombic symmetry term, is analyzed in Appendix A.

IV. H_{c2} IN THE PLANE OF THE MAIN SYMMETRY AXIS

Upper critical field in the $\hat{a}\hat{c}$ plane for a trigonal superconductor was considered in papers[9] and[10] in connection with the Chevrel phase compound $\mathrm{Cu_{1.8}Mo_6S_8}$. We would like to emphasize here the role of the coefficient κ_5.

In the case of a magnetic field lying in the $\hat{a}\hat{c}$ plane the GL differential equation on $\boldsymbol{\eta}$ analogous to (8) is more complicated. It can be somewhat simplified if one assumes

$$\kappa_2 = \kappa_3. \tag{25}$$

This equality comes out in the microscopic calculation of the rigidity coefficients (see Sec. V), it was also presupposed in both[9] and[10]. Conditions (4) become then

$$\kappa_1 > 0,\ \kappa_4 > 0,\ \kappa_5^2 \ < \ \frac{\kappa_{13}\kappa_4}{2},\ -\frac{\kappa_1}{3} < \kappa_3 < \kappa_1. \tag{26}$$

However, even with $\kappa_2 = \kappa_3$ the GL equations allow analytical solution only for $\kappa_2 = \kappa_3 = 0$, $\kappa_5 = 0$, where the upper critical field

$$H_{c2}^{(0)} = -\frac{\Phi_0}{2\pi}\frac{\alpha}{\sqrt{\kappa_1(\kappa_1\cos^2\theta + \kappa_4\sin^2\theta)}} \tag{27}$$

turns out to be the same as in the case of a one-component superconductivity in uniaxial crystals described by the effective mass model (see, e.g.[11]).

The ground state of the Schrödinger equation whose eigenvalue is given by (27) is twice degenerate. And the influence of κ_3 and κ_5 can be accounted for by perturbation theory of degenerate levels. Corresponding theory was constructed in[10]. The formulas, though get more accurate in the second order taking into account crossing of the first-order levels, are barely citable.

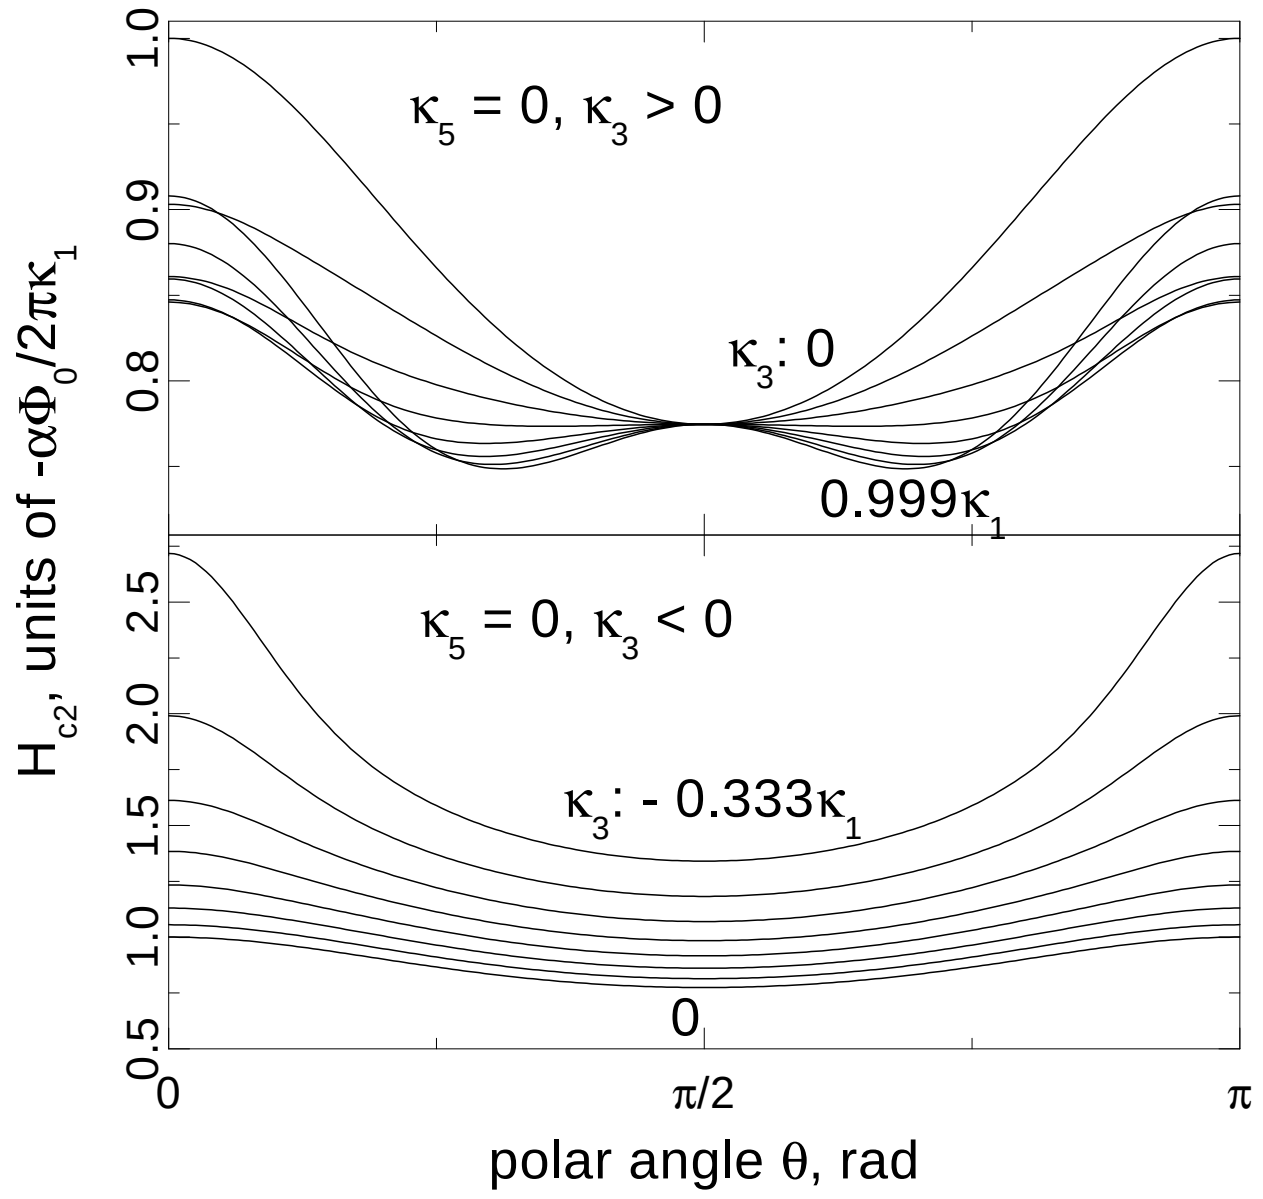

Figure 2: Upper critical field H_{c2} in a hexagonal superconductor with two-dimensional order parameter for a magnetic field lying in the plane of the main symmetry axis as a function of the angle θ between this axis and the magnetic field. Curves in the two sets correspond to equally spaced values of κ_3 running the interval from 0 to $0.999\kappa_1$ (upper plot, from top to bottom) and from 0 to -$0.333\kappa_1$ (lower plot, from bottom to top).

Unexpectedly, a simple first-order expression

$$H_{c2}^{(1)} \ = \ H_{c2}^{(0)} \max\left\{\frac{1}{1+\dfrac{\kappa_3}{\kappa_1}+\dfrac{\kappa_5}{2\widetilde{\kappa}}\sin 2\theta}, \right.$$
$$\left.\frac{1}{1+\dfrac{\kappa_3}{\widetilde{\kappa}}\cos^2\theta - \dfrac{\kappa_5}{2\widetilde{\kappa}}\sin 2\theta}\right\}, \tag{28}$$

where $H_{c2}^{(0)}$ is given by (27) and

$$\widetilde{\kappa} = \kappa_1\cos^2\theta + \kappa_4\sin^2\theta, \tag{29}$$

is in no much worse accord with the values obtained numerically than the bulkiest of those in[10].

Note that variational fit with the trial function $\boldsymbol{\eta} = (\eta_1, \eta_2)e^{-Az^2/2}$ with three free parameters gives[9] an expression which in the domain of applicability of perturbation theory coincides with (28).

The dependence of the upper critical field in a hexagonal crystal (i.e., for $\kappa_5 = 0$) for a magnetic field lying in the $\hat{a}\hat{c}$ plane on the angle θ between the direction of magnetic field and the $\hat{c}$-axis is depicted on Fig. 2 for several values of the coefficient κ_3 from its definition interval (26). κ_4/κ_1 was put equal to 1.67. Only the range of angles from 0 to π is shown because reversing direction of the magnetic field, which corresponds to the substitution $\theta \to \theta+\pi$, does not change the value of H_{c2} resulting

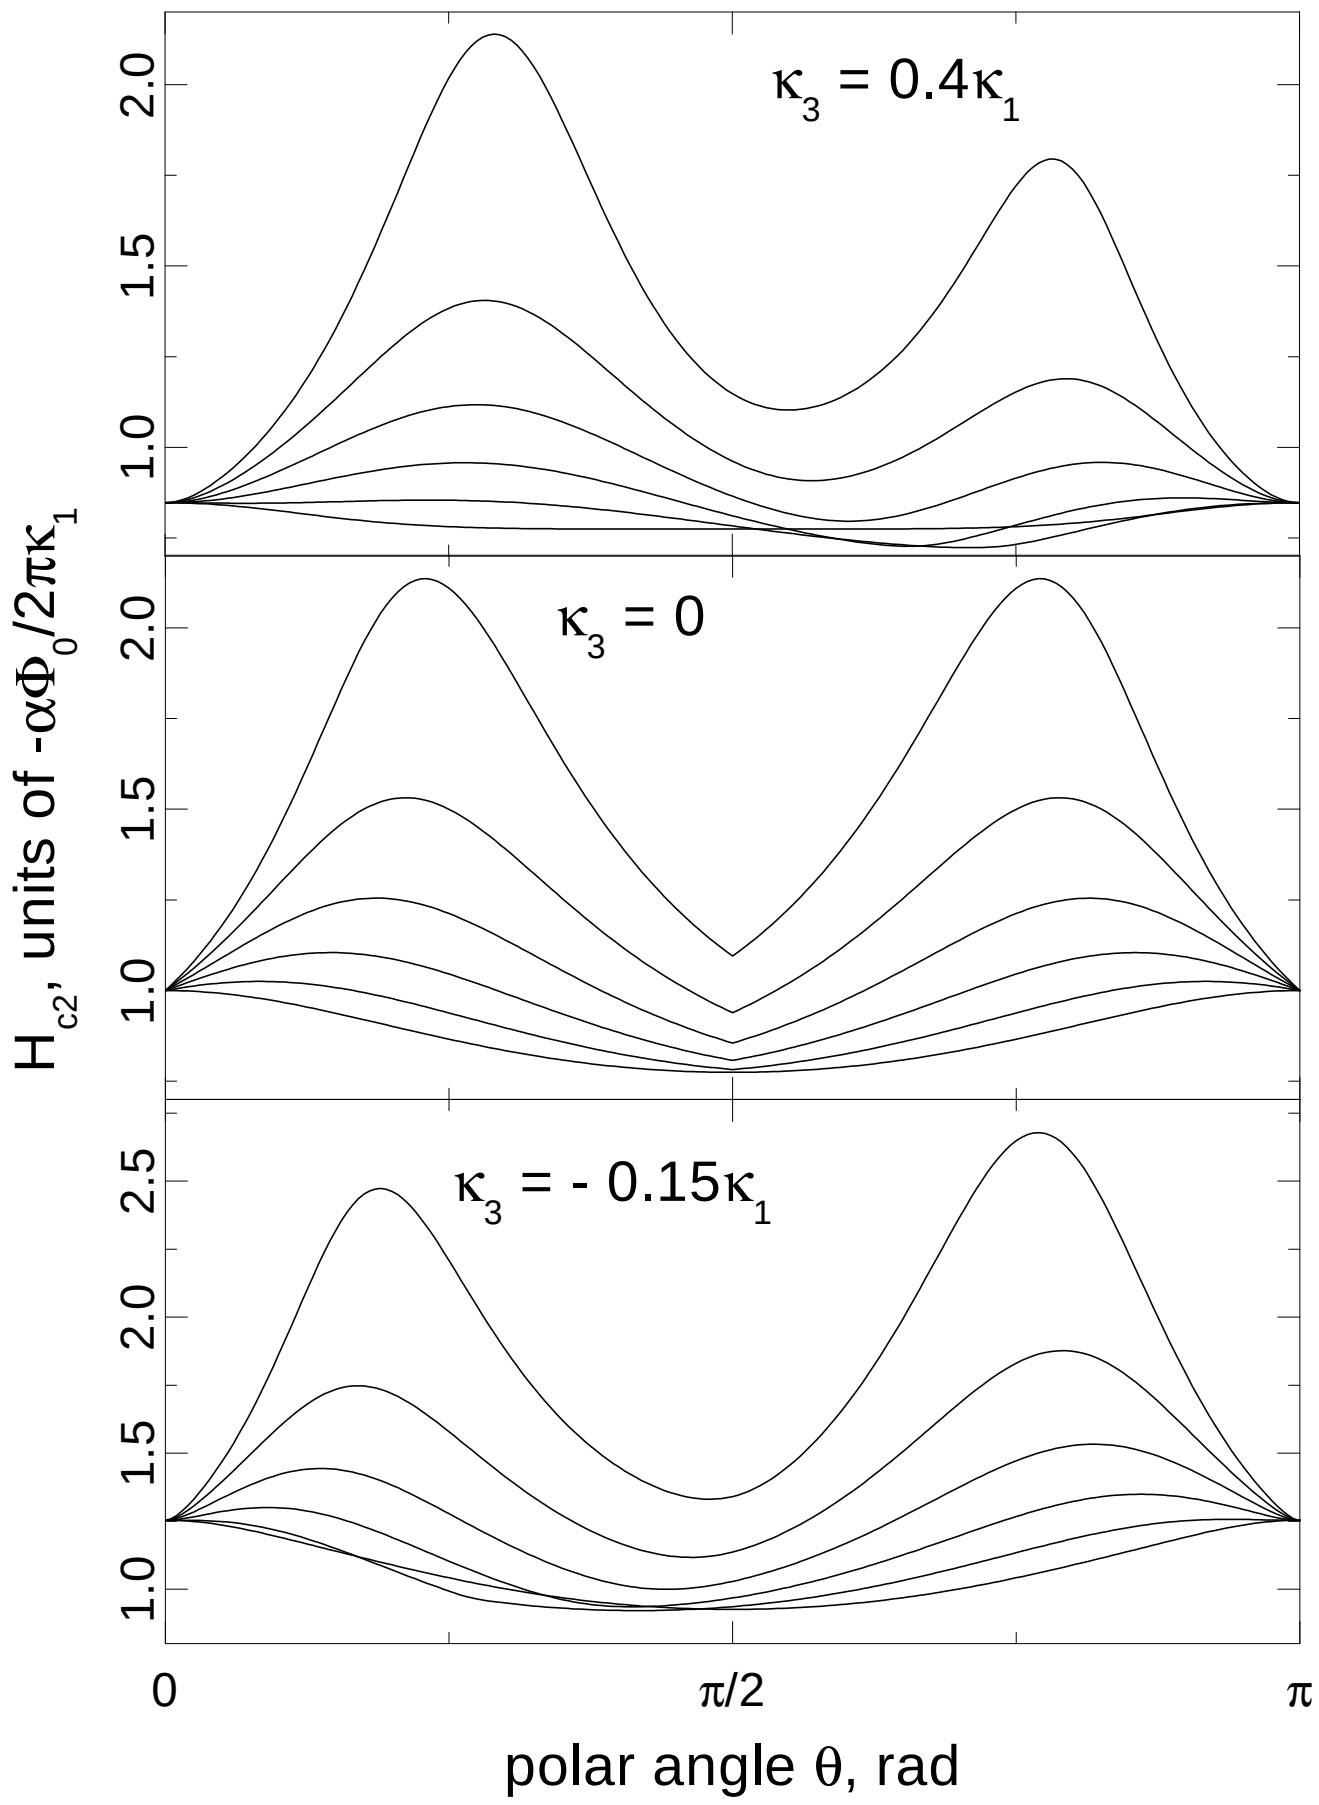

Figure 3: H_{c2} in a trigonal crystal ($\kappa_5 \neq 0$) for $\kappa_3 = 0.4\kappa_1$ (upper plot), $\kappa_3 = 0$ (middle plot) and $\kappa_3 = -0.15\kappa_1$ (lower plot). In each set of the curves the coefficient κ_5 runs over an equally spaced set of values in the interval from 0 (lower curve in the set) to the upper boundary $\sqrt{\kappa_{13}\kappa_4/2}$ of the possible values of κ_5 (upper curve in the plot).

from the functional (1) with (3), meaning that the curve on Fig. 2 should be continued periodically.

The curves in each set correspond to the equally spaced values of the phenomenological coefficient κ_3 running the range between $\kappa_3 = 0$ and $\kappa_3 = 0.999\kappa_1$ (upper plot), and between $\kappa_3 = 0$ and $\kappa_3 = -0.333\kappa_1$ (lower plot) inclusively.

The behavior of H_{c2} with the increase of $|\kappa_3|$ is described (for large $|\kappa_3|$ of course only qualitatively) by (28) with κ_5 put equal to zero. Since

$$\frac{1}{\kappa_1}\Bigg/\frac{\cos^2\theta}{\widetilde{\kappa}} = 1 + \frac{\kappa_4}{\kappa_1}\tan^2\theta \geq 1, \tag{30}$$

we conclude that for $\kappa_3 < 0$, when the first term in (28) is the larger, the curve of the dependence of H_{c2} on θ is scaled with the increase of $|\kappa_3|$ roughly as

$$1/(1 + \kappa_3/\kappa_1) \tag{31}$$

without changing its overall shape. Note also that $H_{c2}(\theta = \frac{\pi}{2})$ then equals (15).

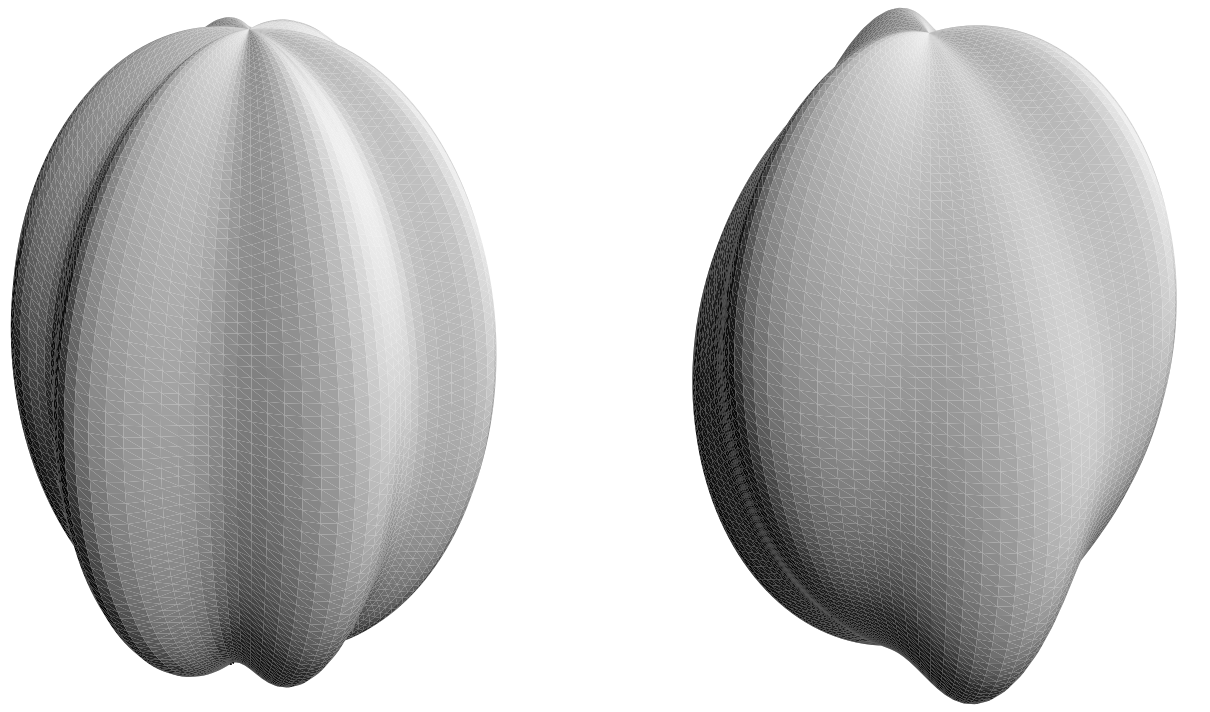

Figure 4: Visualization of hexagonal (left) and trigonal (right) perturbations to an ellipsoidal Fermi surface used to study the qualitative dependencies of the values of the rigidity coefficients on the form of the Fermi surface.

For $\kappa_3 > 0$ the upper critical field is described in the first order of perturbation theory by the second term in (28), and indeed the increase in κ_3 is accompanied by the appearance and growing of a “bump” around $\theta = \pi/2$. The value $H_{c2}(\theta = \frac{\pi}{2})$ equals (14).

Non-zero coefficient κ_5 (trigonality) results in the discrimination between upper and lower parts of a crystal, and thus in the curves $H_{c2}(\theta)$ non-symmetric with respect to the point $\theta = \pi/2$ if also the coefficient $\kappa_3 \neq 0$ (see Fig. 3).

At non-zero κ_5 and κ_3 the curves are characterized by the presence of two maxima in the range $0 < \theta < \pi$ with the heights proportional to κ_5 and the ratio of the heights proportional to $|\kappa_3|$, though at large $|\kappa_3|$ the proportionality of the ratio becomes weaker, so that (28) extrapolated to large $|\kappa_3|$ exaggerates the difference in heights.

A local minimum of $H_{c2}(\theta)$ is achieved between the two maxima at an angle $\theta < \pi/2$ for $\kappa_3 < 0$ and $\theta > \pi/2$ for $\kappa_3 > 0$.

V. RELATIVE VALUE OF THE RIGIDITY COEFFICIENTS $\kappa_1, \kappa_2, \kappa_3, \kappa_4$ AND κ_5

In the weak-coupling BCS theory these coefficients can be calculated[12] as averages over the Fermi surface

$$\frac{\kappa_{i\mu j\nu}}{\kappa_0} = \langle \hat{v}_{\mathrm{F}i}\hat{v}_{\mathrm{F}j}\boldsymbol{\psi}_\mu(\hat{k})\boldsymbol{\psi}_\nu(\hat{k})\rangle_{\mathrm{F}}, \tag{32}$$

where $\boldsymbol{\psi}_\mu(\hat{k})$ are normalized vector basis functions (in the $\mathbf{k}$-space) of the irreducible representation Γ according to which the order parameter

$$\mathbf{d}_{\hat{k}} = \sum_{\mu=1}^{\dim\Gamma} \eta_\mu \boldsymbol{\psi}_\mu(\hat{k}) \tag{33}$$

transforms.

The details of the calculations are placed into Appendix B. Here we describe the conclusions.

Table I: Rigidity coefficients for various basis functions and a spherical Fermi-surface with hexagonal and trigonal perturbations.

Basis $\psi_\mu(\hat{k})$	$\frac{\kappa_1}{\kappa_0}$	$\frac{\kappa_2}{\kappa_0} = \frac{\kappa_3}{\kappa_0}$	$\frac{\kappa_4}{\kappa_0}$	$\frac{\kappa_5}{\kappa_0}$
$(\hat{k}_x, \hat{k}_y)\hat{\mathbf{z}}$	$\frac{1}{5}$	$\frac{1}{5}$	$\frac{1}{5}$	$\frac{16}{105}\alpha_{\rm tr}$
$\hat{k}_z(\hat{k}_x^2 - \hat{k}_y^2, -2\hat{k}_x\hat{k}_y)\hat{\mathbf{z}}$	$\frac{1}{3} + \frac{256}{429}\alpha_{\rm hex}$	$-\frac{256}{429}\alpha_{\rm hex}$	$\frac{1}{3}$	$-\frac{68}{429}\alpha_{\rm tr}$
$\hat{k}_z(\hat{k}_x^3 - 3\hat{k}_x\hat{k}_y^2)\ (\hat{k}_x, \hat{k}_y)\hat{\mathbf{z}}$	$\frac{5}{26} + \frac{56}{4199}\alpha_{\rm hex}$	$\frac{5}{26} + \frac{56}{4199}\alpha_{\rm hex}$	$\frac{3}{13} - \frac{2352}{4199}\alpha_{\rm hex}$	$\frac{12}{221}\alpha_{\rm tr}$
$\hat{k}_z(\hat{k}_x^3 - 3\hat{k}_x\hat{k}_y^2)\ \hat{k}_z(\hat{k}_x^2 - \hat{k}_y^2, -2\hat{k}_x\hat{k}_y)\hat{\mathbf{z}}$	$\frac{9}{34} - \frac{4032}{7429}\alpha_{\rm hex}$	$\frac{3}{34} + \frac{4800}{7429}\alpha_{\rm hex}$	$\frac{5}{17} - \frac{4480}{7429}\alpha_{\rm hex}$	$-\frac{42}{323}\alpha_{\rm tr}$

The symmetry of a crystal can be taken into account in two ways. First, it is necessarily reflected in the symmetry of the Fermi surface of a superconductor. And secondly, it should be complied with by the basis functions $\boldsymbol{\psi}_\mu(\hat{k})$ of the superconducting state. The shape of the Fermi surface (namely, its cross sections) is studied in the dHvA experiments. The basis functions are totally unobservable.

We have modeled the Fermi surface by a sphere (for simplicity of calculation) with superimposed small hexagonal and trigonal perturbations (see Fig. 4):

$$\begin{aligned} f(\hat{k}) &= \alpha_{\rm hex}\Re(\hat{k}_x + i\hat{k}_y)^6 + \alpha_{\rm tr}\hat{k}_z\Re(\hat{k}_x + i\hat{k}_y)^3 \qquad (34) \\ &= \sin^3\theta\left(\alpha_{\rm hex}\sin^3\theta\cos 6\varphi + \alpha_{\rm tr}\cos\theta\sin 3\varphi\right), \end{aligned}$$

where $\alpha_{\rm hex}$ and $\alpha_{\rm tr}$ are the small phenomenological parameters defining the strength of the perturbation.

The factor $\hat{k}_z = \cos\theta$ in the expression for the trigonal part of the perturbation differentiates between the upper and lower halves of the Fermi surface. The form of the upper part of the perturbed surface is schematically shown with the solid curve on Fig. 5, and that of the lower part — with the dashed one. The power of $\sin\theta$ in front of each term is of course a question of convenience, it must only be positive to make the two poles $\theta = 0, \pi$ non-singular.

We have taken four sample bases $\psi_\mu(\hat{k})$ of the irreducible representation E_u of the group D_{3d}. The results are presented in Table I. The complicated fractional values have no physical meaning, — e.g. for an oblate unperturbed Fermi surface they would be different. Does matter the sensitivity of the rigidity coefficients of the superconducting state with a particular basis to the Fermi surface perturbation of a given symmetry.

The first two bases are the most frequent examples for the E_{1u} and E_{2u} irreducible representations respectively of the group D_{6h}[12]. Since both these representations become E_u in the less symmetric group D_{3d}, their bases are valid choices.

The second two bases are simply products of the first two by the function $\hat{k}_z(\hat{k}_x^3 - 3\hat{k}_x\hat{k}_y^2) = \hat{k}_z\Re(\hat{k}_x + i\hat{k}_y)^3$. Since this function is invariant under transformations only from the D_{3d} group and not from D_{6h}, these bases are specific for the E_u representation of the D_{3d} group.

Table I shows that all four bases respond to trigonal perturbation of the Fermi surface, while only the two last respond to hexagonal perturbation, — basis $(\hat{k}_x, \hat{k}_y)\hat{\mathbf{z}}$ does not respond to the latter at all, and for basis $\hat{k}_z(\hat{k}_x^2 - \hat{k}_y^2, -2\hat{k}_x\hat{k}_y)\hat{\mathbf{z}}$ the coefficient κ_4 rests unchanged in the linear order.

VI. DISCUSSION

As we have seen, six-fold modulations $\propto (1 - T/T_c)$ of the upper critical field in the basal plane can be naturally explained in the framework of a usual GL theory in a trigonal unconventional superconductor. Experimentally observed modulations ($|\delta H_{c2}^{hex}/H_{c2}| \lesssim 0.02$) are of the same order of magnitude as trigonal deviations from the hexagonal structure (~ 0.01).

The form of the orientational dependence of H_{c2} as given by the theory rests fairly accurately sinusoidal in almost all the domain of the phenomenological parameters of the GL theory that keep the GL functional positive definite except for the values of both the parameters κ_3 and κ_5 extremely close to the upper limit of their domains.

At the same time, the curves of the angular dependence of resistivity having been observed in the transport experiments[5] and their continuation[14], possessed sharp minima at $\varphi = \pi n/3$ (i.e., at directions of $\mathbf{H} \parallel \mathbf{a}$). Not discussing here the legitimacy of mapping form of $\rho(\varphi)$ onto $H_{c2}(\varphi)$ we remark here that the observed sharp dips can't be accounted for by the present theory of equilibrium upper critical field.

In contrast, the six-fold modulations in the theory developed by Sauls[8] in the framework of hexagonal structure of UPt$_3$ originated from hexagonal in-plane anisotropy of the AFM order parameter $\mathbf{m}_s$ coupled to the superconducting order parameter, on the supposition that $\mathbf{m}_s$ stays almost orthogonal to the external magnetic field.

Although the latter assumption contradicts experiment, the theory managed to account for the change of sign of the modulations with the passing through the

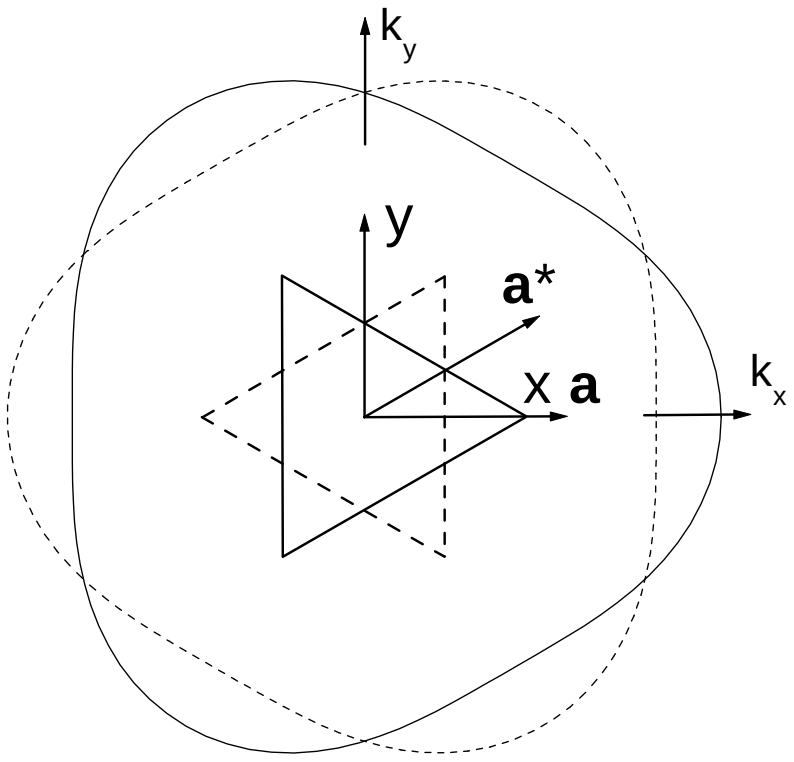

Figure 5: Schematic representation of the orientation of the coordinate system with respect to the crystalline axes. Also shown is the form (in the **k**-space) of the trigonal perturbation to the Fermi-surface.

tetracritical point. Corrections from not exact orthogonality of $\mathbf{m}_s$ to $\mathbf{H}$ also rendered hexagonal modulations non-sinusoidal.

We considered a version of our GL theory with an orthorhombic anisotropy in Appendix A. Upper critical field retained six-fold modulations if the orthorhombic anisotropy was fixed in the direction parallel or perpendicular to the magnetic field, the sign of the modulations changing at the tetracritical point. However, the modulations then became $\propto (1 - T/T_c)^2$, and the trigonal invariant $\propto \kappa_5$ in the GL functional (1) then prevented the intersection of the two curves $H_{c2}(T)$.

Thus experimentally irrelevant hypothesis of $\mathbf{m}_s$ staying perpendicular to $\mathbf{H}$ leads in both theories to similar effects, although six-fold modulations of H_{c2} themselves stem from completely different sources.

Experiments[14] revealed also correlation between the six-fold modulations of the upper critical field in the basal plane of some samples of UPt$_3$ and the appearance of a non-symmetric peak at $\theta = \pi/2$ (i.e., at $\mathbf{H} \perp \hat{c}$) of H_{c2} in the plane passing through the main symmetry axis.

Since UPt$_3$ turned out in reality to have trigonal crystal structure, one *should* expect both six-fold modulations of the upper critical field in the basal plane and some non-symmetry $\theta \leftrightarrow \pi - \theta$ in the plane of the symmetry axis. But again, the form of the curves on Fig. 3 bears little similarity with usual hexagonal curves with superimposed non-symmetric peaks at $\theta = \pi/2$ experimentally observed in the resistivity measurements of[14].

An important and not yet fully understood role, however, is played by the discovered[1] merohedry of UPt$_3$ — division of a sample on a large number of small (∼200-300Å) domains with alternating sign of trigonality.

The existence of such domains probably leaves the conclusion of the modulation of H_{c2} in the basal plane intact, for so six-fold a modulation is shared by all the domains irrespective of the signs of their trigonality. On the other hand, the magnitude of H_{c2} when a field is deflected from the basal plane clearly depends on the direction in which it is deflected — in other words, a trigonal monocrystal does not possess the symmetry $\hat{c} \leftrightarrow -\hat{c}$.

In the investigated samples total numbers of the domains with the opposite signs of trigonality roughly coincided, so one should not probably wonder at the fact that the forms of the experimentally observed[14] and theoretically predicted (Fig. 3) dependencies are in poor agreement. Even the strong non-symmetry $\theta \leftrightarrow \pi - \theta$ of the theoretical curves finds only modest correspondence in the experimental results probably also due to approximately equal number of merohedral domains with the opposite signs of trigonality.

In the end, a few words are to be said on the microscopically obtained qualitative dependence of the trigonal GL coefficient κ_5 on the shape of the Fermi surface. We found that κ_5, which is responsible for all the effects of the trigonal structure in the theory, is proportional to a trigonal contribution to the model Fermi surface. The shape resembling right figure on Fig. 4 was never observed to the author's knowledge in dHvA experiments in UPt$_3$, probably because, as one can note, the cross-section of such a figure in linear order of the trigonal perturbation coincides with that of an unperturbed one.

VII. ACKNOWLEDGMENTS

The authors are grateful to P. Rodiere and A. Huxley for useful conversations and discussion of unpublished data and to J. A. Sauls for the interest in the work and helpful comments. One of the authors (P. K.) is also grateful to J. Flouquet for the granted opportunity to complete the work at the Center for Nuclear Research in Grenoble.

Appendix A: VARIATIONAL METHOD FOR H_{C2} IN THE BASAL PLANE

Main features of the upper critical filed (23) can be seen on a variational fit with the trial function

$$\boldsymbol{\eta} = \begin{pmatrix} \eta_{\parallel} e^{-\sqrt{\kappa_1/\kappa_4}\, z^2/2} \\ \eta_{\perp} e^{-\sqrt{\kappa_{123}/\kappa_4}\, z^2/2} \end{pmatrix}, \tag{A1}$$

where $\eta_\perp$ and $\eta_\parallel$ are to be found from minimization of the GL functional with respect to them. The result then turns out to be just a truncated sum of the second order perturbation theory.

Even simpler though for this particular form of the trial function is[7] to substitute it directly into Eq. (9), which then becomes an algebraic equation on $\eta_\perp$, $\eta_\parallel$. From the condition of vanishing of the corresponding determinant one then gets for the eigenvalue

$$(\lambda - \sqrt{\kappa_1 \kappa_4})(\lambda - \sqrt{\kappa_{123}\kappa_4}) = \sqrt{\kappa_1\kappa_4}\sqrt{\kappa_{123}\kappa_4}A^2, \tag{A2}$$

where

$$A^2 = \frac{2\kappa_5^2}{\kappa_4\sqrt[4]{\kappa_1\kappa_{123}}}\frac{(\sqrt{\kappa_1}-\sqrt{\kappa_{123}})^2}{(\sqrt{\kappa_1}+\sqrt{\kappa_{123}})^3}\cos^2 3\varphi. \tag{A3}$$

Using the definition (7) of λ, one arrives at an equation

$$\left(H - H_{c2\|}(T)\right)\left(H - H_{c2\perp}(T)\right) = A^2H^2, \tag{A4}$$

which describes six-fold modulation of the upper critical field. E.g., supposed that $\kappa_{23} > 0$, i.e., that the superconducting state with the order parameter parallel to the magnetic field arises first, we find

$$H_{c2} \approx H_{c2\|}\left(1 + \frac{A^2H_{c2\|}}{H_{c2\|} - H_{c2\perp}}\right), \tag{A5}$$

or, substituting (14) and (15),

$$H_{c2} \approx H_{c2\|}\left(1 + 2\frac{\kappa_5^2}{\kappa_4}\sqrt[4]{\frac{\kappa_{123}}{\kappa_1}}\frac{\sqrt{\kappa_{123}}-\sqrt{\kappa_1}}{(\sqrt{\kappa_{123}}+\sqrt{\kappa_1})^3}\cos^2 3\varphi\right). \tag{A6}$$

For $\kappa_{23} < 0$ we get an analogous expression with the opposite sign in front of the corrections.

It is interesting to remark that a six-fold modulation of H_{c2} in the basal plane of a trigonal crystal appears also in the presence of an orthorhombic anisotropy (see, e.g.,[11],[12]) in the direction fixed parallel or perpendicular to the magnetic field. The corresponding term was introduced to the GL theory to account for the splitting of the superconducting transition in UPt$_3$.

With such a term one of the fields $H_{c2\|}(T)$ or $H_{c2\perp}(T)$ becomes $\propto (1 - T/T_{c*})$ rather than $\propto (1 - T/T_c)$, where the splitting between T_c and T_{c*} is proportional to the magnitude of the orthorhombic anisotropy. Eq. (A4) is still valid then and produces six-fold corrections (A5) to H_{c2}, though proportional to $(1 - T/T_c)^2$ unlike (A6), where they are linear. In such a version of the theory, however, the term $\propto \kappa_5$ in the GL functional leads to the repulsion of the two lines of $H_{c2}(T)$ so that instead of a tetracritical point one has a splitting $\propto A$.

Appendix B: CALCULATION OF THE RIGIDITY COEFFICIENTS

Relative values of the rigidity coefficients is convenient to study with the model dispersion law of electrons

$$\epsilon_{\mathbf{k}} = \frac{k^2}{2m} + 2\epsilon_{\mathrm{F}}f(\hat{k}), \tag{B1}$$

where $f(\hat{k})$ is a small perturbation with a symmetry determined by the symmetry of the crystal. For simplicity we will consider all the expressions up to leading term in f. The form of the perturbation of interest to us is (34) as stated in the main text.

The Fermi-surface is defined by $\epsilon_{\mathbf{k}} = \epsilon_{\mathrm{F}}$, whence we obtain its equation in the parameterization of the unit vector $\hat{k}$

$$\mathbf{k}(\hat{k}) = k_{\mathrm{F}}(1 - f(\hat{k}))\hat{k}, \tag{B2}$$

where $k_{\mathrm{F}} = \sqrt{2m\epsilon_{\mathrm{F}}}$. Making use of the value of $\hat{k}$ in terms of the spherical angles θ, φ one obtains for the element of the Fermi surface

$$|\partial_\theta\mathbf{k} \times \partial_\varphi\mathbf{k}|d\theta d\varphi = k_{\mathrm{F}}^2(1 - 2f(\hat{k}))\sin\theta d\theta d\varphi. \tag{B3}$$

The unit vector $\hat{v}_{\mathrm{F}}$ of the Fermi velocity $\mathbf{v}_{\mathrm{F}} = \boldsymbol{\partial}_{\mathbf{k}}\epsilon_{\mathbf{k}}|_{\mathrm{F}}$ can be calculated from (B1) to be

$$\hat{v}_{\mathrm{F}} = \hat{k} + \partial_{\hat{k}}f - \hat{k}\left(\hat{k}\partial_{\hat{k}}f\right). \tag{B4}$$

Thus the averaging (32) over the Fermi-surface may be written as

$$\begin{aligned}\frac{\kappa_{\mu i\nu j}}{\kappa_0} &= \frac{\langle(1 - 2f(\hat{k}))\hat{v}_{\mathrm{F}i}\hat{v}_{\mathrm{F}j}\boldsymbol{\psi}_\mu(\hat{k})\boldsymbol{\psi}_\nu(\hat{k})\rangle_{\hat{k}}}{\langle 1 - 2f(\hat{k})\rangle_{\hat{k}}} \qquad \text{(B5)}\\ &= \left(1 + 2\langle f(\hat{k})\rangle_{\hat{k}}\right)\langle\hat{k}_i\hat{k}_j\boldsymbol{\psi}_\mu(\hat{k})\boldsymbol{\psi}_\nu(\hat{k})\rangle_{\hat{k}}\\ &+ \Big\langle\big[\hat{k}_i\big(\partial_{\hat{k}_j}f - \hat{k}_j(\hat{k}\partial_{\hat{k}}f) - \hat{k}_jf\big)\\ &+ \hat{k}_j\big(\partial_{\hat{k}_i}f - \hat{k}_i(\hat{k}\partial_{\hat{k}}f) - \hat{k}_if\big)\big]\boldsymbol{\psi}_\mu(\hat{k})\boldsymbol{\psi}_\nu(\hat{k})\Big\rangle_{\hat{k}}.\end{aligned}$$

Calculating the integrals in (B5) with the bases functions described in the main text, one arrives at Table I.

---

[1] D. A. Walko, J.-I. Hong, T. V. Chandrasekhar Rao, Z. Wawrzak, D. N. Seidman, W. P. Halperin, M. J. Bedzyk, Phys. Rev. B **63**, 054522 (2001).

[2] M. J. Graf, S.-K. Yip, and J. A. Sauls, Phys. Rev. B **62**, 14393-14402 (2000).

[3] A. Huxley, P.Rodiere, D.McK. Paul, N. van Dijk, R. Cu-

bitt, and J. Flouquet, Nature (London) **406**, 160 (2000).

[4] T. Champel and V. P. Mineev, Phys. Rev. Lett. **86**, 4903-4906 (2001).

[5] N. Keller, J. L. Tholence, A. Huxley, J. Flouquet, Phys. Rev. Lett. **73**, 2364-7 (1994); N. Keller, J. L. Tholence, A. Huxley, J. Flouquet, Physica C **235-240**, 2441-2 (1994).

[6] L. I. Burlachkov, Zh. Eksp. Teor. Fiz. **89**, 1382-8 [Sov. Phys. JETP **62**, 800-3] (1985).

[7] V. P. Mineev, Annales de Physique **19**, 367-84 (1994).

[8] J. A. Sauls, Phys. Rev. B **53**, 8543-8 (1996).

[9] L. I. Burlachkov, Physica C **166**, 25-8 (1990).

[10] Yu. S. Barash, A. V. Galaktionov, Zh. Eksp. Teor. Fiz. **100**, 1699-710 [Sov. Phys. JETP **73**, 939-44] (1991).

[11] V. Mineev, K. Samokhin, *Introduction to Unconventional Superconductivity,* (Gordon and Breach, 1999).

[12] J. A. Sauls, Adv. Phys. **43**, 113-41 (1994).

[13] For brevity we do not write the normalization factors which should be such as to $\langle \boldsymbol{\psi}_\mu(\hat{k})\boldsymbol{\psi}_\nu(\hat{k})\rangle_{\hat{k}} = \delta_{\mu\nu}$.

[14] P. Rodiére, PhD thesis, CEA-Grenoble, 2001 (unpublished).